

FABRICATION AND EVALUATION OF A MACHINE FOR SEPARATING FIBER FLAX

A. M. DRESS*

ABSTRACT

Flax stalks usually considered a waste product which may be utilized by separation into marketable fiber and shive. The fiber can be used for applications such as composites and paper. Separation of traditional long line fiber from fiber flax stalks is a rigorous and expensive process that requires the stalk to be biologically degraded (retted) before processing. A local machine for removing flax fiber from chopped seed flax straw has been manufactured at a private workshop in kafr El-sheikh Governorate during summer season of 2015. The manufactured machine consists of three main devices namely: feeding and breaking device, scutching and hackling device and cleaning device. The manufactured machine has been evaluated under three straw moisture contents of 10.2, 13.2 and 15 %, three deram schell speeds of 500, 650 and 800 rpm and five feeding roller speeds of 1, 1.5, 2, 2.5 and 3 m/s. The Separation efficiency, fiber length and fineness, machine Productivity, consumed Energy, and quality of fiber were studied. The obtained results can be summarized as follows: The maximum separation efficiency of flax fiber (82.13%) and fiber fineness (191.6 mm/mg) was obtained at straw moisture content of 10.2%, feeding roller speed of 1m/sec and derma schell speed of 800 r.p.m. The fiber Length (92.8cm) was obtained at straw moisture content of 10.2%, feeding roller speed of 1m/sec and derma schell speed of 500 r.p.m. The lowest value of energy consumption was (1 kw) recorded at straw moisture content of 10.2%, feeding roller speed of 1m/s and dearm schell speed of 500 r.p.m. It is recommended for the operators of the manufactured separation machine to operate it at straw moisture content of 10.2%, feeding roller speed of 1 m/s and derma schell speed of 800 r.p.m to obtain the optimum performance.

Keywords: *flax, separating fibers, design, cleaning, consumed energy, machine evaluation.*

* Assoc. Prof., Ag. Eng. Dept., Fac. of Agric., AL-Azhar University- Assuit.

INTRODUCTION

Flax considers the most important economic oil and fiber crops in all over the world as well as in Egypt. Flax (*Linum usitatissimum* L) fibers for cloth originated about 10,000 years ago. Ancient Egyptians placed scenes of flax cultivation on the walls of tombs, and bobbies were mummified in flax shrouds (Oelke et al., 1987). The flax stalk consists of fiber bundles located between the epidermis or bark surface and an inner wood core (shive). The fiber bundles in flax stalks are usually separated into individual fibers before use. Two general types of flax are grown- fiber flax and seed flax. Fiber is extracted from fiber flax stalks and divided into two classes. The short, damaged fiber called tow is sometimes known as cottonized flax and is used in lower quality fabrics. Tow is also blended with other products such as cotton to make fabric. The fiber separating processes in many steps such as retting, drying, breeking and separating so, they need a hard effort and high cost. Retting is the process of rotting away the inner stalk, leaving the outer fibres intact

Mollog (2000) reported that fiber percentage in the flax straw increases from flowering to maturity from around 17 to 25%, it remains constant at around 16% in linseed.

Eichhom (2001) found that the mechanical properties of flax: density 1.5 g/cm^3 , break 2.7- 3.2%, tensile strength 345-1035 Mpa, young's modulus 27.6 Gpa. While these two natural fibers are similar, the properties of the plant as well as the mandatory processing to obtain fibers vary greatly. Flax stalks contain approximately 30% fiber and 70% trash.

Mohanty et al., (2001) remembered that the flax density was 1.5 g/cm^3 , tensile strength was 345–1100 (Mpa) young's modulus 27.6 (Gpa) and elongation at Break was 2.2 – 3.2%.

Fouda et al (2011) found that the separation efficiency of flax fibers 74% with vibration movement at sieve speed of 2.8m/s, feeding rate of 100kg/h and moisture content of 7.75%. The fibers length of 89.5cm were obtained at sieve speed of 1.6m/s, feeding rate of 100kg/h and moisture content of 7.75%. The best degree of fiber fineness (182.6 mm/mg) was at sieve speed of 2.8m/s, feeding rate of 100 kg/hr and moisture content of 7.75%.

Anthony (2002) run three studies to determine the cleaning effectiveness of gin machinery in separating flax fiber from chopped seed flax straw. His three studies used various combinations of cylinder cleaners and lint cleaners and flax raw material chopped to about 5.1 cm in length, retrieval of pure fiber (corrected for shive content) ranged from a low of 7.1% to a high of 12.8%.

Anthony (2005) evaluated the potential of several machines to remove flax fiber from chopped seed flax straw. Then, a new machine that incorporated the principles of several machines was built and tested. The initial version of the machine did not yield the desired 80% fiber purity, so more saw cylinders were added. The most effective version produced 13.8% yield out of a possible 20% fiber with a purity of 81.4% .The yield can be improved with additional modifications to the machine.

Ismail (2009) indicated that the degree of fibers fineness decreased by the increase in straw moisture content., the highest value of fiber fineness of 129.74 mm/mg was obtained at straw moisture content of 8.42%, while the lowest value of fiber fineness of 126.63 mm./mg was obtained at straw moisture content of 12.6%. The Egyptian farmers do not have any small-scale machines to help them for separating flax fibers. Raising the income of the farmer, achieved by using a simple mechanical system using for separating flax fibers, which, reduces all losses and save transporting costs. Consequently, reduces the problems face Egyptian farmers farmer sells their crops after harvesting with low prices, and also affected the main physical and mechanical properties of flax fibers were. The main objective of the present is to manufacture a local machine for separating flax fibers and evaluate the performance of this machine under different operating conditions.


MATERIALS AND METHODS

A machine for flax fibers separation was fabricated at a private rural workshop in kafr El-sheikh Governorate during the summer season of 2015. The unit consists of the following main parts:

- a- Feeding and breaking mechanism.
- b- Scutching and hackling mechanism.
- c- Cleaning mechanism.
- d- The machine frame on which al the components assembled

e- Electric power motor and transmission.

The machine frame made of angle iron (4×4cm) with dimensions of 153cm length, 60 cm width and 85 cm height as shown in fig1.

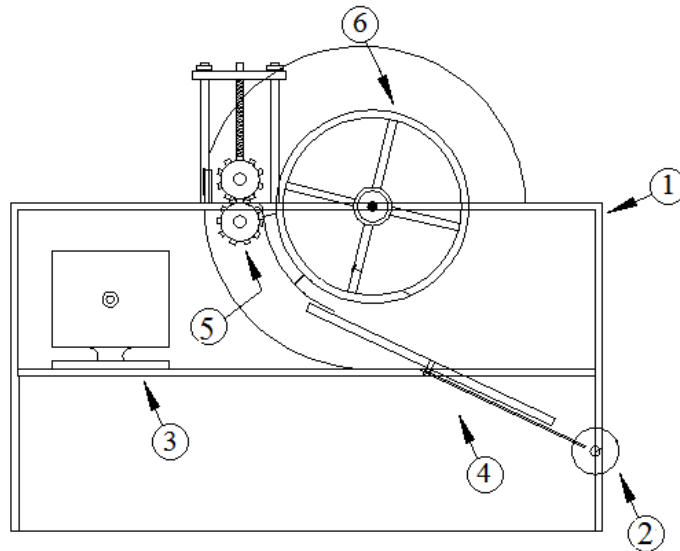

- | | |
|----------------------|----------------------------------|
| 1- frame | 4- cleaning device |
| 2- decentralized cam | 5- feeding and breaking device |
| 3- electric motor | 6- scutching and hackling device |

Figure1. Side view of the fabricated machine for separating flax fibers .

The feeding and breaking device consists of two cylinder of grooved surface with 60 cm length; 10 cm diameter overlaped 1cm. The function of feeding and breaking mechanism feed is to and crack the inner wood of the flax straw. The machine is powered by 2 hp electric motor. A gearbox was used for power transmission and speed reduction. as shown in fig 2.

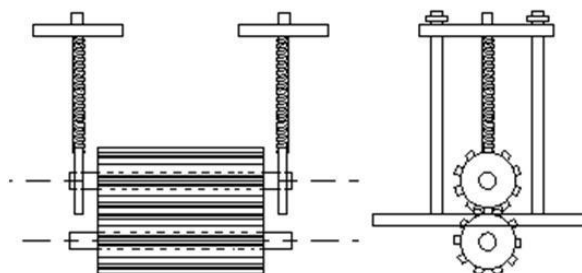


Figure2. Elevation and side view of the feeding and breaking device in machine for showing the overlap of the cylinder surface tooth.

The scutching and hackling device consists of a vicious surface cylinder with 60 cm diameter. The mechanism turned at 500- 850 r.p.m rotational speed and equipped with 4 iron poles shaped as a comb teeth, This pullets were fixed on the outer surface of the cylinder assembled parallel to the main axis of the cylinder. The main function of this device is to separate the flax fibers from the inner bark of the flax stalks. It was powered by the electric motor and a set of pulleys in addition to conveyor belts as shown in fig. 3.

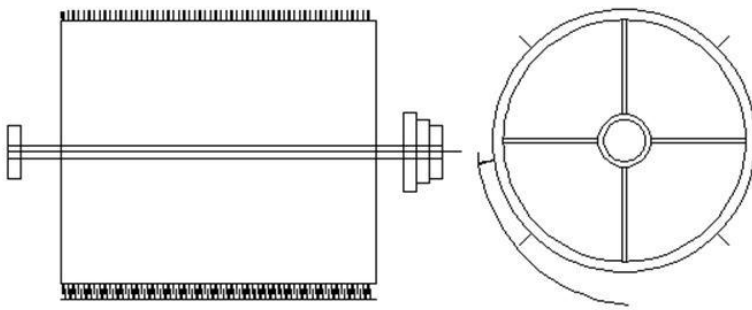


Figure3. Side view of the scutching and hackling device .

The cleaning device consists of a flat surface steel sheet with 80×60 cm dimensions that assembled with inclination of about 25 degree and provided with a series of rectangular openings its dimensions of 10×0.5 cm. The mechanism moves reciprocating that generat vibrating by decentralized cam. This device converts the rotational motion into reciprocating movement to clean the linen fibers from the wood pieces and internal bark before discharge from the machine as shown in fig. 4.

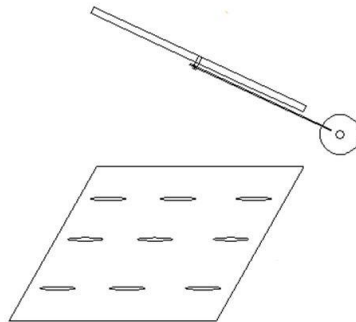


Figure4. The cleaning device in machine for separating flax fibers fabricated.

Field experiments were conducted to evaluate the performance of the manufactured separating machine under the following parameters:-

- 1- Three straw moisture contents (10.2, 13.2 and 15%).
- 2- Fives feeding roller speeds (1, 1.5, 2, 2.5 and 3 m/s).
- 3- Three derma schell speeds (500,650, and 800 r.p.m).

After harvesting and separating the seeds from flax plants the stalks were connected and sent for retting stalk. The retting process takes about 7-15 days, and then plants were dried in the yard for a few days. After that breaking process was undertaken in order to crush by passing stalks into breaking machine through fluted rollers. Cutting stalks into small pieces of bark is called shaves. Then the broken stalks transferred [n to the cleaning machine to separate the fibers from the shaves with rotating sieve and finally releasing the flax fibers from stalks. Some physical properties of flax are shown in table 1.

Table (1): Some physical properties of straw flax.

Physical properties	Main value
Plant height, mm	1140
Technical length, mm	989
Stalk diameter, mm	3.45
Straw yield, ton/fed	3.28
Length of root zone, mm	120-150
Fibres percent %	20 %
Woody- shaves %	80 %

Measurements:

1. Straw moisture content:

Straw moisture content was determined after retting times at different three stages of drying by taking a five straw samples randomly after 10,15 and 20 days from retting these samples were dried in the oven at 70 °C for 24 hours. The straw moisture content was calculated according to (Fouda, 2011) using the following equation.

$$M = \frac{M_{ws} - M_{ds}}{M_{ws}} \times 100$$

Where:

M = Straw moisture content, %

M_{ws} = Wet straw weight, g.

M_{ds} = Dry straw weight, g.

2. Separating efficiency:

Separating efficiency was estimated by using the following equation.

$$S_p = \frac{W_B - W_A}{W_B} \times 100$$

Where:

S_p = separating efficiency, %

W_B = Total weight of wood pieces, kg

W_A = Total weight of wood pieces with fibres, kg

3. Machine Productivity:

Time of separating flax fibres process was measured by means of a stop watch. The capacity of the machine was calculated as follows:

$$P_m = \frac{W}{T}$$

Where

P_m : Machine Productivity, kg h^{-1} .

W : Mass of sample, kg.

T : Separating time ,h.

4. Consumed energy (CE)

The required electric power was measured for cleaning and grading process. The required electric power was calculated to (*Lockwood and Dunstan, 1971*) by using the following equation.

$$RP = \sqrt{3} \times V \times I \times \eta \times \cos \theta$$

Useful power = load – no load).

Where

RP : The required power ,W.

V : Potential difference, Voltage (3 phase = 380 voltage).

I : Line current strength, Amperes.

$\cos \theta$: Power factor, equal 0.84.

η : Mechanical efficiency assumed (95%).

A digital clamp meter and Voltmeter were used for measuring current intensity and voltage respectively.

5. Fiber fineness:

Fiber fineness in metrical number, was determined according to (Radwan and Momtaz, 1966) using the following equation.

$$N_m = \frac{N - L}{G} \times 100$$

Where:

- N_m = metrical number (mm/mg)
- N = No. fibres (20 fibres each 10 cm).
- L = length of fibres in mm, 2000.
- G = weight of fibres, mg.

6- Long fiber percentage:

Long fibre length was measured using a scale meter (model).And determined (very long. Medium, short and very short) of flax fibres.

7. Long fibre strength (tension force):

Long fiber strength was measured by using prissily implement according to(Radwan and Momtaz ,1966) using the following formula:

$$F_s = \frac{N \times L \times C_f}{G}$$

Where:

- F_s = Fibbers strength, mm. N/mg.
- N = Number of 20 fibres tested (fibers' each 10 cm).
- L = length of tested fibers, mm.
- G = weight of tested fibres, mg.
- C_f = Mean of the tensile force for breaking an individual fibers, N.

RESULTS AND DISCUSSIONS**1- Separation efficiency:**

The separation efficiency is an important parameter to evaluate the performance of separating machine. Table 2 and fig 5 show the efficiency of the manufactured separating machine as affected by straw moisture content, feeding roller speed and derma Schell speed. Data indicated that

the increment in straw moisture content from 10.2 to 15 %. decreases the separation efficiency of the manufactured machine from 71.36 to 42.23 %.

Table (2) Mean values of Separation efficiency, machine Productivity for fiber flax separation at different moisture content, feeding roller speed and derma Schell Speed.

M. C , %	feeding roller Speed ,m/sec	Separation efficiency %			machine Productivity ,kg/hr		
		Derma Schell Speed, r.p. m					
		500	650	800	500	650	800
10.2	1	74.2	78.7	82.13	38.2	37.5	36.2
	1.5	73	75.1	77.4	43.51	42.7	38.6
	2	71.8	73.6	75.1	46.2	45.5	43.4
	2.5	70	71.2	73	49	48	45.6
	3	67.8	69.3	70.8	52.8	52	48.8
13.2	1	65.3	68.7	70.15	47.95	46.06	44.3
	1.5	64	66.2	65.1	53.76	52.1	47.4
	2	63.1	65	64.6	57.2	55	53.6
	2.5	60.4	61.8	63.1	60.8	57.3	56.12
	3	57.5	59.4	61.2	64.66	63.7	60.5
15	1	45.8	49.2	54.6	52.69	50.9	49
	1.5	44.1	45.7	53	60.7	57.2	56.1
	2	42	44.1	51	65	61.6	58.9
	2.5	40	42.8	49.7	68.3	64.2	63
	3	39.25	40.3	45.8	72.1	67.35	65.12
Mean values of derma Schell Speed		58.55	60.74	63.77	55.52	53.40	51.10
Mean values of straw moisture content	10.2	71.36	73.58	75.68	45.94	45.14	42.52
	13.2	62.06	64.22	64.83	56.87	54.83	52.38
	15	42.23	44.42	50.82	63.75	60.25	58.42
Mean values of feeding roller Speed	1	61.76	65.53	68.96	46.28	44.82	43.16
	1.5	60.36	62.33	65.16	52.65	50.66	47.36
	2	58.96	60.9	63.63	56.13	54.03	51.96
	2.5	56.8	58.6	61.93	59.36	56.5	54.9
	3	54.85	56.33	59.26	63.18	61.016	58.14

The maximum separation efficiency was obtained with the straw moisture content of 10.2% for all the feeding roller and derma schell speeds. The data also observed that increasing the feeding roller speed tends to decrease the separation efficiency. The feeding roller speed of 1 m/s gave the maximum average value of separation efficiency of 75.68 % at straw moisture content of 10.2 % and derma schell speed of 650 r.p.m. On the other hand, the obtained average values of separation efficiency were 74.2, 78.7 and 82.2 % at derma Schell speeds of 500, 650 and 800 r.p.m with straw moisture content of 10.2 % and feeding roller speed of 1 m/s.

Generally, it is clear that the straw moisture content of 10.2 %, feeding roller speed of 1 m/s and derma schell speed of 800 r.p.m gave the maximum separation efficiency of 82.1% however, the minimum separation efficiency of 39.3 % was recorded with the straw moisture content of 15.0 %, feeding roller speed of 3m/s and derma schell speed of 500 r.p.m .

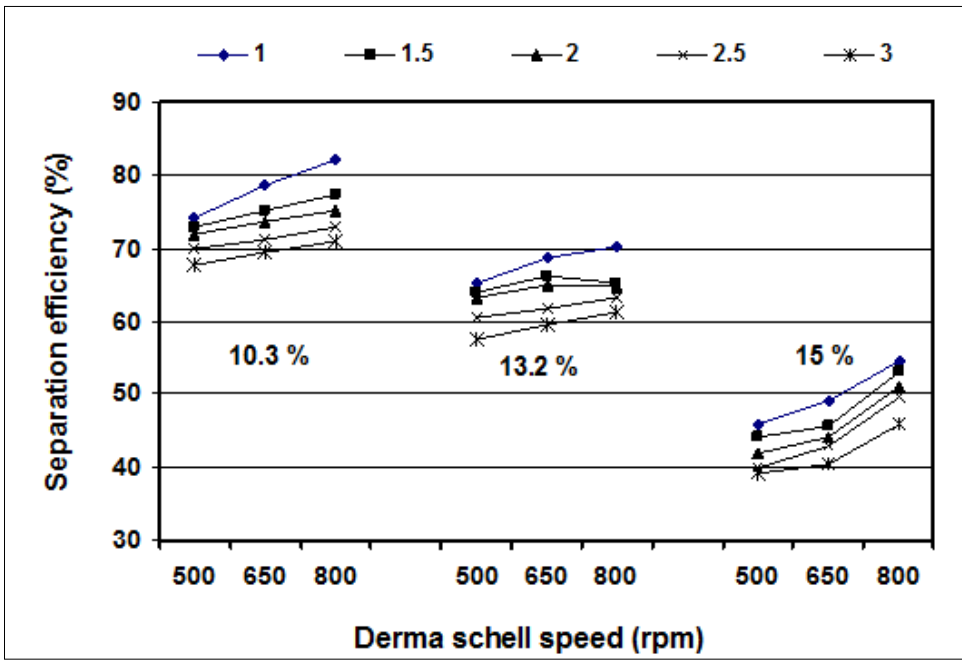


Fig.5: Effect of straw moisture content, feeding roller speed and derma schell speed on separation efficiency.

2- Machine Productivity:

The machine Productivity is an important parameter to evaluate the performance of separating machine. Table 2 and fig 6 show the Productivity of the manufactured separating machine as affected by straw moisture content, feeding roller speed and derma Schell speed. Data illustrated that the increment in straw moisture content from 10.2 to 15 % tend to increase the machine Productivity from 45.94 to 63.75 kg/h. The maximum values machine Productivity was obtained with the straw moisture content of 15% for all the feeding roller and derma schell speeds. The data also revealed that the machine productivity increased

when the feeding roller speed increased for all the straw moisture contents and derma shell speeds. The feeding roller speed of 3 m/s gave the maximum average value of machine Productivity of 72.1 kg/h at straw moisture content of 15 % and derma shell speed of 500 r.p.m. On the other hand, the obtained average values of machine Productivity were 72.1, 67.35 and 65.12 kg/h at derma shell speeds of 500, 650 and 800 r.p.m respectively, with straw moisture content of 15 % and feeding roller speed of 3 m/s. Generally, it is clear that the straw moisture content of 15 %, feeding roller speed of 3 m/s and derma Schell speed of 500 r.p.m gave the maximum machine Productivity of 72.1 kg/h but, the minimum Productive machine of 36.2 kg/h was recorded with the straw moisture content of 10.2 %, feeding roller speed of 1m/s and derma Schell speed of 500 r.p.m. These results may be due to the increasing derma Schell speed leading to increase the losses in flax fiber.

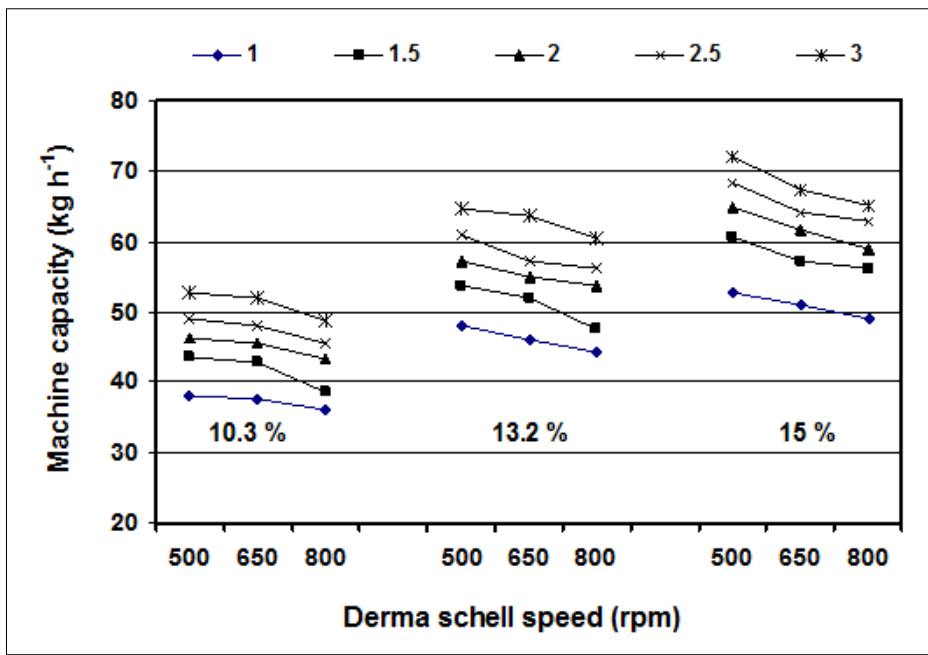


Fig.6: Effect of straw moisture content, feeding roller speed and derma schell speed on machine Productivity.

3 - Consumed Energy:

There was a significant effect of straw moisture content, feeding roller speed and derma schell speed on the Consumed energy as shown in Table

3 and fig 7 It is evident that, the Consumed energy decreased by decreasing the straw moisture content for all the feeding roller and derma schell speeds. The straw moisture content of 10.2 % consumed the minimum value of energy of 1 kw at feeding roller speed of 1 m/s and derma Schell speed of 500 r.p.m. These results may be due to increasing derma schell speed and feeding roller speed led to increase consumed energy in unit time through the material of flax stalk. The feeding roller speeds of 1, 1.5, 2, 2.5 and 3 m/s gave consumed energy of 1, 1.2, 1.3, 1.4 and 1.6 kw, respectively, at straw moisture content of 10.2 % and derma schell speed of 500 r.p.m.

Table (3) Mean values Consumed energy, fineness fiber, mm/mg for separation fiber flexes at different moisture content, feeding roller speed and derma Schell Speeds.

M. C , %	feeding roller Speed ,m/sec	Consumed energy, kw			fineness fiber ,mm/mg		
		Derma Schell Speed, r.p. m					
		500	650	800	500	650	800
10.2	1	1	1.1	1.3	158.2	175.3	191.6
	1.5	1.2	1.3	1.5	155.8	172.8	188.3
	2	1.3	1.4	1.7	153.3	170.1	185.6
	2.5	1.4	1.6	1.9	150.4	169	182.7
	3	1.6	1.8	2	147.1	166.8	180
13.2	1	1.19	1.28	1.46	155	169.3	180.9
	1.5	1.38	1.4	1.65	153.7	166.2	177.6
	2	1.45	1.6	1.72	152.1	164	175
	2.5	1.62	1.78	1.85	150	161.5	171.8
	3	1.85	1.95	2.05	145.1	157.2	167.2
15	1	1.37	1.5	1.65	148.2	160	169.3
	1.5	1.5	1.75	1.85	145.6	157.3	166.1
	2	1.65	1.82	1.9	142.3	155	163.4
	2.5	1.75	1.96	2.15	140.1	152	161.2
	3	1.92	2.12	2.32	137	148.5	157
Mean values of derma Schell Speed		1.48	1.58	1.76	148.92	163	174.51
Mean values of straw moisture content	10.2	1.3	1.44	1.68	152.96	170.80	185.64
	13.2	1.5	1.6	1.74	151.18	163.64	174.5
	15	1.64	1.7	1.88	142.64	154.56	163.4
Mean values of feeding roller Speed	1	1.18	1.29	1.35	153.8	168.2	180.6
	1.5	1.36	1.48	1.55	151.7	165.43	177.33
	2	1.46	1.6	1.7	149.23	163.03	174.66
	2.5	1.59	1.78	1.88	146.83	160.83	171.9
	3	1.79	1.95	2.01	143.06	157.5	168.06

The consumed energy increased by about 60% when the feeding roller speed increased from 1 to 3 m/s. However, the consumed energy increased by increasing the derma schell speed for all straw moisture contents and feeding roller speed. The consumed energy decreased by 20% when the derma schell speed decreased from 850 to 500 r.p.m at straw moisture content of 15% and feeding roller speed of 3 m/s. Generally, the minimum values of the consumed energy were recorded with straw moisture content of 10.2%, feeding roller speed of 1.0 m/s and derma schell speed of 500 r.p.m.

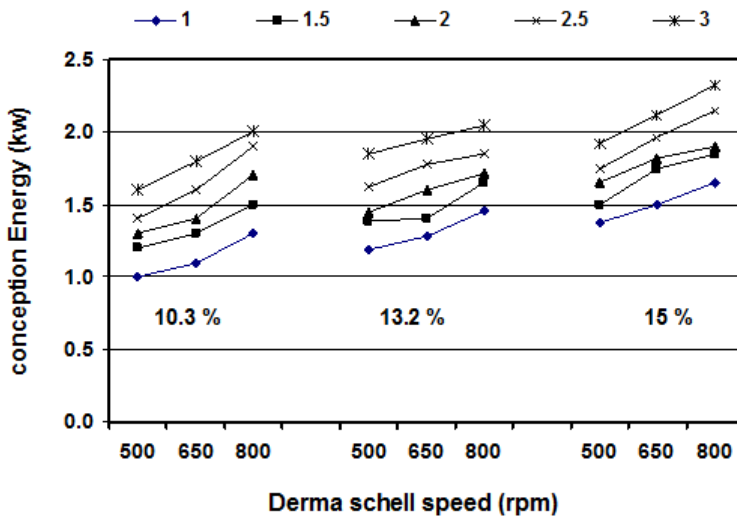


Fig.7: Effect of straw moisture content, feeding roller speed and derma schell speed on Consumed energy.

4- Quality of fiber:

a- Fineness degree of fiber:

There was a significant effect of straw moisture content, feeding roller speed and derma schell speed on the fiber fineness as shown in table 3 and fig 8 . It is evident that, the fiber fineness decreased by increasing the straw moisture content for all the feeding roller and derma schell speeds. The straw moisture content of 10.2 % attained the maximum value of fiber fineness of 191.6 mm/mg at feeding roller speed of 1 m/s and derma schell speed of 800 r.p.m. These results may be due to increasing derma schell speed that facilitates the rotation derma schell in unit time through

the flax stalk material. The feeding roller speeds of 1, 1.5, 2, 2.5 and 3 m/s gave fiber fineness of 175.03, 172.30, 169.67, 167.37 and 164.63 mm/mg, respectively. It is clear that, increasing the feeding roller speed tended to decrease the fiber fineness for all the straw moisture contents and derma schell speeds. However, the feeding roller speed of 1m/s gave maximum value of fiber fineness. On the other hand, the derma schell speed of 800 r.p.m recorded the maximum value of fiber fineness of 191.6 % compared with the other speeds for straw moisture content 10.2% and feeding roller speed of 1m/s. Finally, the results indicated that the maximum value of fiber fineness was obtained with straw moisture content of 10.2%, feed roller speed of 1m/s and derma schell speed of 800 r.p.m.

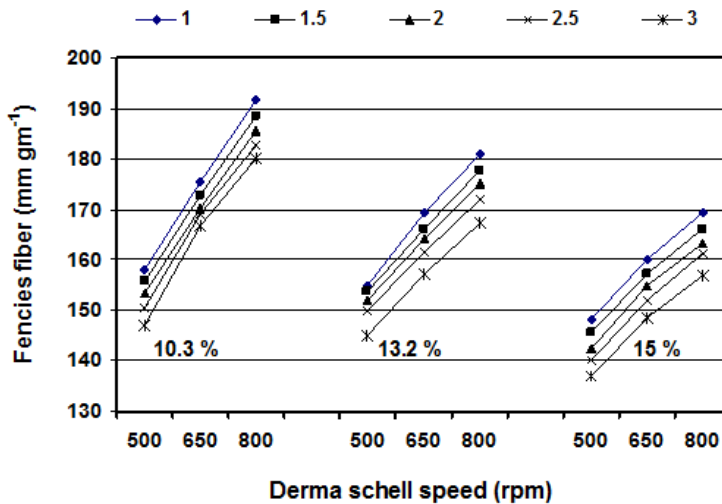


Fig.8: Effect of straw moisture content, feeding roller speed and derma schell speed on fineness fibre.

b -length of fiber:

The fiber length ranged from 61.3 to 92.8 cm at variation of straw moisture content from 10.2 to 15%, feeding roller speed from 1 to 3 m/s and derma schell from 500 to 800 r.p.m as shown in table 4 and fig 9 .The results indicated that increasing the straw moisture content tended to decrease the fiber length for all feeding roller and derma schell speeds.The fiber length decreased by 20% when the straw moisture content increased from 10.2 to 15%. The data also demonstrated that the

fiber length decreased by increasing the feeding roller speed for all the straw moisture contents and derma schell speeds. The feeding roller speed of 1.0 m/s attained the maximum average value of fiber length (90.1 cm) at straw moisture content of 10.2%. These results may be due to increasing material stalk flax opening in derma Schell in unit time. On the other hand, increasing the derma schell speed tended to decrease the fiber length for all straw moisture contents and feeding roller speeds. Generally, the maximum average value of fiber length (92.8 cm) was obtained with straw moisture content of 10.2%, feeding roller speed of 1.0 m/s and derma schell speed of 500 r.p.m

Table (4) Mean values length of fiber, tension force of fiber, Mpa for separation fiber flex at different moisture content, feeding roller speed and derma Schell Speed

M. C , %	feeding roller Speed ,m/sec	length of fiber ,cm			Tension force of fiber, Mpa		
		Derma Schell Speed, r.p. m					
		500	650	800	500	650	800
10.2	1	92.8	90.3	87.2	1280	1160	1020
	1.5	92.1	88.2	86.5	1291	1172	1032
	2	91.6	86.7	85	1305	1180	1041
	2.5	91	84.2	83.2	1317	1191	1055
	3	89.1	81.9	80	1326	1201	1076
13.2	1	85.5	83.1	80	1650	1590	1510
	1.5	83.1	82	79	1661	1595	1518
	2	82	80.7	77.2	1675	1615	1531
	2.5	80	78.3	75.6	1687	1627	1540
	3	79	76.1	73.1	1696	1641	1562
15	1	77.4	73.2	69.8	1952	1930	1882
	1.5	75	71.8	66.7	1958	1934	1887
	2	73.2	70.1	65.1	1965	1940	1893
	2.5	70.8	68	63	1975	1944	1898
	3	68.2	65.3	61.3	1987	1953	1892
Mean values of derma Schell Speed		82.05	78.66	75.51	1648.33	1578.2	1489.13
Mean values of straw moisture content	10.2	91.32	86.26	84.38	1303.8	1180.8	1044.8
	13.2	81.92	80.04	76.98	1673.8	1613.6	1532.2
	15	72.92	69.68	65.18	1967.4	1940.2	1890.4
Mean values of feeding roller Speed	1	85.23	82.2	79	1627.33	1560	1470.66
	1.5	83.4	80.66	77.4	1636.66	1567	1479
	2	82.26	79.16	75.76	1648.33	1578.3	1488
	2.5	80.6	76.83	73.93	1659.66	1587.33	1497.66
	3	78.76	74.43	71.46	1669.66	1598.33	1510

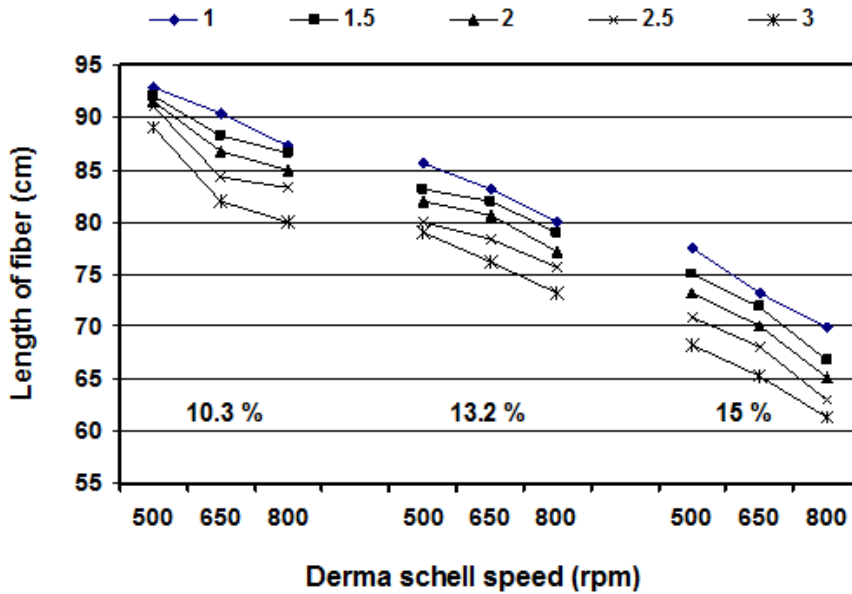


Fig.9: Effect of straw moisture content, feeding roller speed and derma schell speed on length of fiber.

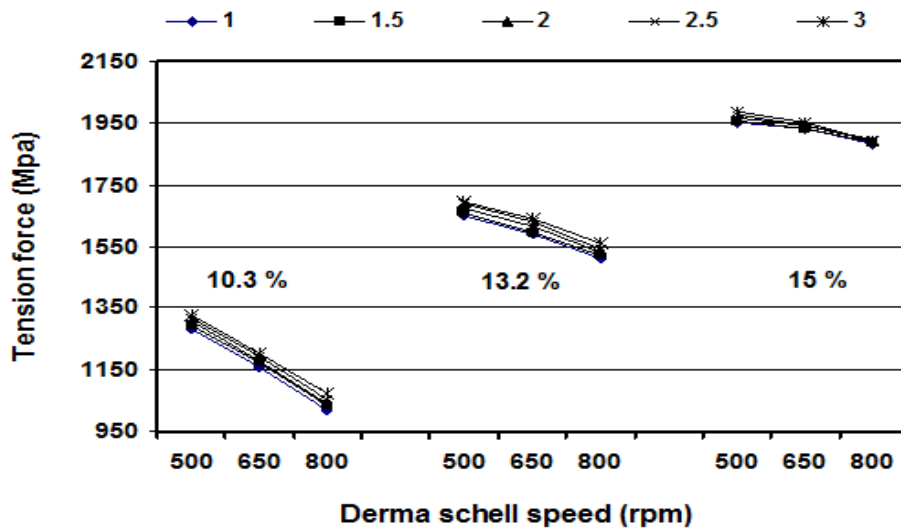


Fig.11: Effect of straw moisture content, feeding roller speed and derma schell speed on tension force of fiber.

c-Tension force of fiber :

Tension force of fiber is considered an important parameter to evaluate the performance of separating machine. Table 4 and fig 11 show the effect of straw moisture content, feeding roller speed and derma schell speed on the tension force of fiber. Data indicated that the increase in straw moisture content from 10.2 to 15 % tend to increase the tension force of fiber from 1176.5 to 1932.7 Mpa . The maximum tension force of fiber was obtained with the straw moisture content of 15% for all feeding roller and derma schell speeds. The data also showed that the tension force of fiber increased by increasing the feeding roller speed from 1.0 to 3 m/s for all the straw moisture contents and derma schell speeds. The feeding roller speed of 3 m/s gave the maximum average value of tension force of fiber 1987 Mpa at straw moisture content of 15 % and derma schell speed of 500 r.p.m. On the other hand, the obtained average values of tension force of fiber were 1987, 1953 and 1892 Mpa at derma schell speeds of 500, 650 and 800 r.p.m with straw moisture content of 15 % and feeding roller speed of 3 m/s. Generally, it is clear that the straw moisture content of 15 %, feeding roller speed of 3 m/s and derma schell speed of 500 r.p.m gave the maximum tension force of fiber 1987 Mpa but, the minimum value of fiber tension force 1020 Mpa was recorded with the straw moisture content of 10.2 %, feeding roller speed of 1m/s and derma schell speed of 800 r.p.m. These results may be due to the increase of derma schell speed that facilitates the rotation derma schell in unit time through the stalk flax material Lead to Lack of fiber withstand tensile forces.

CONCLUSION

The present study concluded the main following points:

1. The manufactured separating machine had a good performance in separating and cleaning fiber flax where, the machine productivity reached 72.1 kg/h, separating efficiency 82.13%. Whereas, the fiber fineness degree, tension force and length were 191.6mm/mg, 1987 Mpa and 92.8 cm, respectively.
2. The results showed that decreasing both straw moisture content and feeding roller speed tend to increase separating efficiency, fiber fineness and length for all the derma schell speeds.

3. Results also, indicated that the increment in derma schell speed tend to increase the separating efficiency, consumed energy and fiber fineness while, machine productivity, fiber length and tension force decreased for all straw moisture contents and feeding roller speeds.
4. The data demonstrated that the straw moisture content of 10.2%, feeding roller speed of 1 m/s and derma schell speed of 800 r.p.m recorded the maximum values of separating efficiency of 82.13%, fiber fineness of 191.6 mm/mg and fiber length of 92.8 cm.
5. The minimum value of the consumed energy for separating the flax stalks of 1 kw was obtained with straw moisture content of 10.2%, feeding roller speed of 1 m/s and derma schell speed of 500 r.p.m.
6. It is recommended for the operators of the manufactured separating machine to operate it at straw moisture content of 10.2%, feeding roller speed of 1 m/s and derma schell speed of 800 r.p.m to obtain the optimum performance.

REFERENCES

- Anthony, W.S. (2003).** Device to separate contaminants from cotton and flax. Article · January 2003 with 20 Reads
- Anthony, W.s. (2005).** Development of machines to separate fiber and shave from seed flax straw. Applied Engineering in Agriculture. 21(6):1057-1063.
- Anthony,W.S.(2002).**Separation of fiber from seed flax straw. Applied Engineering in Agriculture 18(2):227-233.
- Chancellor, W. J. 1981.** Substituting information for energy in agricultural. Trans. ASAE Paper No. 0001- 2351.
- Eichhom, S.I.et al. (2001)** .Journal of Materials Science. Review Current international research into cellulosic fibres and composites. (36):2107-2131.
- Fouda,T.Z.,Badr,S.E.,Derbala,A.A.,andA.E.Elashry(2011).**
 Manufacture and performance evaluation of a local machine for separating flax fibers. Annual Conference of the Misr Soc. Of Ag. Eng. 26-27 October

- Ismail(2009).** The technological properties of flax fibers and the methods of estimating them, El-Felaha Jour. 46(5): 466-476. (In Arabic).
- Lockwood,F.B.and R.Dunstan (1971).** Electrical engineering principles. Heinemann Educational Books. Ltd. London.
- Mohanty,A.K., M. Misra and L.T.Drzal. (2001).** Surface modifications of natural fibers and performance of the resulting biocomposites: An overview. Composite Interfaces 8(5):313-343.
- Molloy,R.M. (2000).** A study of the plant, fiber and seed development in flax and linseed (linum usitatissimum) grown at a range of seed rates. Journal of Agricultural Science, (135): 361-369.
- Oelke, E.S. Johnson, P. Ehrhardt, and V. Comstock, (1987).** From flax straw to linen fiber. Agricultural fact sheet 3339.Minncsota Extension Service, University of Minncsota. St. Paul, Minn.
- Radwan, B.R.H. and A. Momtaz(1966).** The technological properties of flax fibers and the methods of estimating them, El-felaha Jour.46 (5):466-476.(in Arabic).

الملخص العربي

تصنيع وتقييم آلة محلية الصنع لفصل ألياف الكتان

د. عبد الفتاح محمود محمد دريس*

يعد محصول الكتان أحد أهم محاصيل الألياف في مصر وكثير من دول العالم لدخوله في العديد من الصناعات مثل الورق والمنسوجات والملابس والحبال والأخشاب فضلا عن استخلاص زيت بذرة الكتان منه غير ان عملية فصل الألياف عن بقايا السيقان تعد واحدة من اكبر المشكلات التي تواجه المزارع المصري والتي تضطره الى بيع المحصول لمراكز وشركات خاصة باسعار زهيدة تؤدي الى إنخفاض العائد الربحي للمزارع لذا كانت وما زالت تلك المشكلة بؤرة اهتمام الباحثين من خلال تقديم التكنولوجيا اللازمة لفصل الياف الكتان بكفاءة عالية وبتكاليف منخفضة لذلك كان الهدف الرئيس من هذه الدراسة هو تصنيع وتقييم الأداء لآلة محلية الصنع لفصل ألياف الكتان عن بقايا السيقان ، تتكون هذه الآلة المصنعة من جهاز (وحدة) للتغذية والتكسير وجهاز لفصل الألياف وجهاز للتنظيف (فصل الألياف عن البقايا) حيث أن الطريقة التقليدية المتبعة هي استخدام آلة لكل مرحلة مما يزيد من الجهد والتكاليف . وقد تم تقييم أداء الآلة لتحديد الظروف الملائمة للحصول على أفضل أداء لها من خلال دراسة العوامل التالية .

*استاذ الهندسة الزراعية المساعد - كلية الزراعة - جامعة الأزهر - أسيوط.

- ١ - ثلاثة مستويات من المحتوى الرطوبى لسيقان الكتان (١٠.٢ ، ١٣.٢ ، ١٥%) .
- ٢ - خمس سرعات خطية لدرفيل التغذية والتكسير (١ ، ١.٥ ، ٢ ، ٢.٥ ، ٣ م / ث) .
- ٣ - وثلاث سرعات دورانية لدرفيل التنظيف (٥٠٠ ، ٦٥٠ ، ٨٠٠ لفة / دقيقة) .

وقد تم دراسة تأثير العوامل السابقة على المتغيرات التالية.

كفاءة الفصل لالياف الكتان- السعة الانتاجية لالة - الطاقة المستهلكة- جودة الالياف (نعومة الالياف- طول الالياف- متانة الالياف).

ويمكن تلخيص النتائج المتحصل عليها كمايلي:

- ١ . بلغت السعة الانتاجية لآلة الفصل المصنعة ٧٢.١ كجم/ ساعة وكفاءة الفصل ٨٢.١٣ % ونعومة ومتانة وطول الألياف ١٩١.٦ م/م، ١٩٨٧ ميجا بسكال، ٩٢.٨ سم على الترتيب مما يجعلها مناسبة لفصل الياف الكتان لكفائتها العالية وارتفاع جودة المنتج.
- ٢ . ارتفعت قيم كلا من كفاءة الفصل ونعومة وطول الألياف بإنخفاض كل من المحتوى الرطوبى لسيقان الكتان والسرعة الخطية لدرفيل التغذية والتكسير.
- ٣ . زيادة سرعة درفيل الفصل أدت إلى زيادة كفاءة الفصل والطاقة المستهلكة ونعومة الألياف بينما قلت كل من طول ومتانة الألياف ونتاجية الآلة.
- ٤ . أوضحت النتائج أن كل من المحتوى الرطوبى لسيقان الكتان ١٠.٢ % وسرعة درفيل التغذية ١ م/ث وسرعة درفيل الفصل ٨٠٠ لفة /دقيقة أعطت أعلى القيم لكفاءة الفصل ٨٢.١٣ % ، ونعومة الألياف ١٩١.٦ م/م، وطول الألياف ٩٢.٨ سم .
- ٥ . أقل قيمة للطاقة المستهلكة فى فصل ألياف الكتان كانت ١ كيلوات/ساعة عند محتوى رطوبى ١٠.٢ % وسرعة تغذية ١ م/ث وسرعة فصل ٥٠٠ لفة / دقيقة.
- ٦ . توصي الدراسة باستخدام آلة الفصل المصنعة فى فصل ألياف الكتان عند محتوى رطوبى لسيقان الكتان ١٠.٢ % وسرعة خطية لدرفيل التغذية ١ م / ث، وسرعة دورانية لدرفيل الفصل ٨٠٠ لفة/ دقيقة للحصول على أعلى القيم لكفاءة الفصل وجودة المنتج .